



# Biosynthesis of Copper Nanoparticles by Cultures from Collection of Microorganisms

Lyudmila I. Zaynitdinova\*, Javlon J. Tashpulatov, Nikolay A. Lazutin,  
Rokhila N. Juraeva, and Aziza M. Mavjudova

Institute of Microbiology, Uzbekistan, 100128, Tashkent, A.Kadyri street, 7B, Uzbekistan

**Abstract:** Biogenic production of copper nanoparticles by bacteria and fungi presents certain scientific and applied interest. In this regard, the ability to synthesize copper nanoparticles by microorganisms from the culture collection of the Institute of Microbiology, which were isolated from polluted areas, was studied. Twenty-one fungal strain and eight bacterial strains were screened, and the biosynthetic activity of representatives of *Pseudomonas* genus, as the most active biosynthetic of copper nanoparticles, was studied in a comparative aspect. The biosynthetic activity was determined 24-72 hours after adding standard solutions of  $\text{CuSO}_4$  of different concentration (25-50 mg/l by  $\text{Cu}^{++}$ ) to the culture liquid. The formation of nanoparticles was recorded by changing the color of the solution, as well as using UV spectroscopy and atomic force microscopy (AFM). Two strains of *Fusarium oxysporum* and one strain of *Penicillium* sp. were found to be the most active among the tested micromycetes. The formation of cubic copper nanoparticles and needle-like structures with a diameter of 800 nm and a length of 40 microns, which were formed as a result of aggregation of cubic nanoparticles with a size of 300-400 nm, has been established. All the tested bacteria showed the ability to synthesize copper nanoparticles, while *Pseudomonas stutzeri* and *Pseudomonas* sp. 23 strains expressed the greatest activity and obtained nanoparticles showed high stability. It was also noted that an increase in the initial concentration of copper ions in solution from 25 mg/l to 50 mg/l leads to an increase in the size of the resulting nanoparticles. Based on results of the UV-spectroscopy and AFM microscopy a database of microbial strains synthesizing copper nanoparticles was established, which may be used in future studies.

**Keywords:** Biosynthesis, Microorganisms, Copper Nanoparticles, *Fusarium*, *Pseudomonas*.

## 1. INTRODUCTION

One of the earliest studies on production of the metal nanoparticles by means of microorganisms (bacteria) was reported in 1964 [1]. But the electrochemical method was supposed as the most efficient for synthesis of large amounts of copper nanoparticles (CuNPs) within short period of time. Nevertheless, nowadays production of metal nanoparticles by living organisms has certain advantages compared to electrochemical one, such as environmental safety and conformity of size and shape [2, 3]. Metal nanoparticles possess different useful properties and are widely used in certain areas. There are many studies reported on antimicrobial activity of nanoparticles, including bacteriocidal activity of copper ions upon wide

spectrum of microorganisms. Recently several reviews were published, which stipulated receipt of metal nanoparticles with use of microorganisms isolated from different ecological niches [4-8]. A great number of organisms are reported as producers of different metal nanoparticles: Ag, Au, Cd, Cu, Fe, Pb, Pd, Pt, Se, Zn, Zr and so on. Among those organisms are bacteria [5], fungi [9], yeasts [6], viruses [10], microalga [11], alga [12] and plant extracts [13].

Copper nanoparticles represent certain interest due to their antimicrobial, catalytic, electrical, optical and other properties. Varshney with colleagues have reported application of nonpathogenic strain of *Pseudomonas stutzeri* for the fast method of biological synthesis for

Received: March 2023; Revised: November 2024; Accepted: December 2024

\* Corresponding Author: Lyudmila I. Zaynitdinova <zajn-lyudmila@yandex.ru>

production of 8-15 nm spherical CuNPs [14]. The innovative approach for synthesis of CuNPs by bacteria *Pseudomonas stutzeri*, earlier isolated from soil, resulted in receipt of 50-150 nm cubic shaped CuNPs [15]. Nowadays research activities on application of living organisms for production of metal nanoparticles, including copper, become extremely interesting. Thus, the aim of this work was screening of the culture collection of industrially important microorganisms of the Institute of Microbiology (Tashkent, Uzbekistan) for efficient producers of CuNPs.

## 2. MATERIALS AND METHODS

Strains of microorganisms preserved at the culture collection of industrially important microorganisms of the Institute of Microbiology (Tashkent, Uzbekistan) were used. Cultivation of fungi and bacteria was conducted on two times diluted Czapek-Dox, Mandels and beef extract peptone (BEP) nutrient media, respectively. Aliquots of copper sulfate 25 and 50 mg/l (for copper ions) were added to the cultural liquid of microorganisms. Mixture of cells and copper ions were incubated at the rotary shaker at 180 rpm and 28 °C for 24-72 h. Formation of the copper nanoparticles was visually monitored by change of the color of the solutions. Strains were selected according to their resistance towards different pollutants, including heavy metals, and ability to biosorption of metals as well, since the ability to produce metal nanoparticles is considered as a protective function of the microorganisms [16, 17]. UV-spectroscopic studies were conducted on a spectrophotometer SPECORD 210 (Germany) within range 190-1000 nm. The morphology of copper nanoparticles was studied using an atomic force microscope Agilent 5500 (USA) at the room temperature.

## 3. RESULTS AND DISCUSSION

Modern nanotechnologies are based on development of the reliable, non-toxic, ecologically safe technologies for the production of metal nanoparticles of the wide range of chemical composition, size, synchronized monodispersity, which is mainly possible to achieve by use of biological resources. Several reviews provided in details an information about isolation of the suitable microorganisms from different sources (soil, water, sewages, culture collections) [4, 8].

The culture collection of industrially important microorganisms of the Institute of Microbiology comprises a number of different strains both bacteria and fungi isolated from mines, flotation tails, industrial and household wastes and sewages, polluted soils and waters and so on. Based on analysis of available data several cultures were selected for the screening of ability to produce CuNPs. Filamentous fungi are more resistant towards mutations and possess ability to synthesize different nanoparticles. Selected fungal strains were preliminarily cultivated on nutrient medium containing copper salt. Analysis of selected collection cultures revealed among them several fungal strains capable to produce CuNPs (Table 1). The maximum activity among screened cultures was observed at *Penicillium* sp. 1, *Fusarium oxysporum* 1, and *Fusarium oxysporum* 2.

**Table 1.** Screening for CuNPs producing ability among selected fungal strains.

No.	Culture	Cultivation time (h)		
		24	48	72
1.	<i>Aspergillus niger</i>	-	-	-
2.	<i>Aspergillus terreus</i> 33	-	+	+
3.	<i>Aspergillus terreus</i> 4	-	-	+
4.	<i>Aspergillus terreus</i> 11	-	-	-
5.	<i>Aspergillus glaucus</i>	-	-	-
6.	<i>Aspergillus flavus</i>	-	-	-
7.	<i>Aspergillus versicolor</i>	-	-	+
8.	<i>Aspergillus albus</i>	-	-	-
9.	<i>Aspergillus oryzae</i>	+	+	+
10.	<i>Acremonium</i> sp.	-	+	+
11.	<i>Cladosporium cladosporioides</i>	-	-	-
12.	<i>Cladosporium</i> sp.	-	-	-
13.	<i>Alternaria</i> sp.	-	-	-
14.	<i>Penicillium</i> sp. 1	+	+	+
15.	<i>Trichoderma harzianum</i>	+	+	+
16.	<i>Alternaria pluriseptata</i>	+	+	+
17.	<i>Penicillium</i> sp. 2	-	+	+
18.	<i>Trichurus terrophilus</i>	+	-	-
19.	<i>Nocardia</i> sp.	-	-	-
20.	<i>Fusarium oxysporum</i> 1	+	+	+
21.	<i>Fusarium oxysporum</i> 2	+	+	+

Visual observation revealed that light blue color characteristic for the ions of  $\text{Cu}^{2+}$  disappears in the cultural liquid of *Penicillium* sp. and solution acquires light green-yellowish color. Formation of CuNPs by *Penicillium* sp. was determined by UV-spectroscopy methods at the initial concentration of copper ions 100 mg/l (Figure 1).

The absorption bands, differing by intensity, were formed at  $\lambda_{\text{max}} = 260$  nm in both samples, regardless of the used nutrient medium. UV-spectrum of the strain cultivated on Czapek-Dox medium (sample 6) revealed a small shoulder at  $\lambda_{\text{max}} = 700$  nm, testifying presence of  $\text{Cu}^{2+}$  traces; whereas cultivation on Mandels medium (sample 3) presented no such change.

Morphology of the test samples was studied by AFM method. It was established that systems medium+fungus+ $\text{Cu}^{2+}$  have both nano- and microstructure, the shape of nanoparticles is cubic. Sample 3 is characterized by formation of

needle structures with diameter 800 nm and length 40 micron, which are produced as a result of aggregation of cubic nanoparticles with sized 300-400 nm (Figure 2).

There many reports are available on a wide variety of the fungi-producers of metal nanoparticles [3, 18-22]. Microscopic fungi are less susceptible to mutagenic factors like ions of metals, including heavy ones, and at the same time possess ability to synthesize different compounds, including metal nanoparticles. Nevertheless, there is no consensus on biological mechanism of the metal nanoparticles production. It is general assumption that there is no evidence that some specific type of protein or carbohydrate or lipid or any other molecule is the main factor responsible for production of the metal nanoparticles [23]. In these regards, apparently, proteins play fundamental role in production of CuNPs [2]. On the other hand, it was established that fungal enzymes affect the production of metal nanoparticles, and not only stability [3].

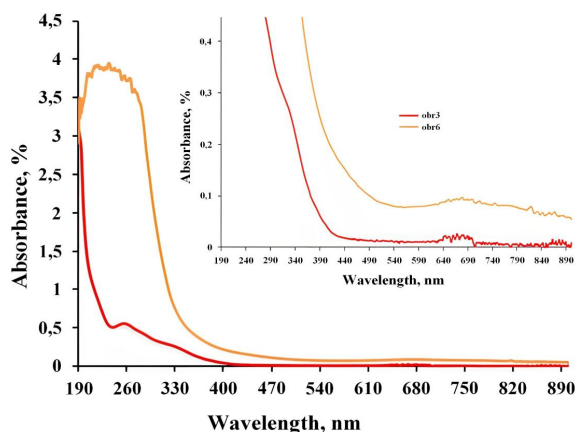


Fig. 1. UV-spectra of systems at different concentrations of CuNPs.

It is well known that bacteria may serve as perspective producers of metal nanoparticles [24-29]. Metal nanoparticles of the bacteria origin proposed for use in different fields of industry. Therefore, screening of the culture collection for potential bacterial producers of CuNPs was essential. Study on selected collection cultures of bacteria, earlier isolated from the polluted areas, established that maximum CuNPs producing activity was determined among strains related to *Pseudomonas*, *Bacillus* and *Acinetobacter* species (Table 2). *Acinetobacter* is not known as active producer of CuNPs, but it participates in formation of the other nanoparticles. Thus,

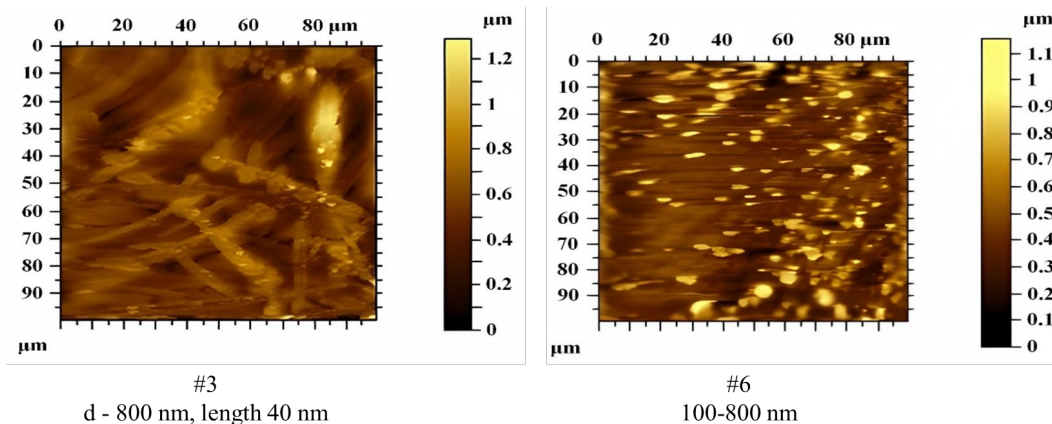


Fig. 2. Morphology of the test samples.

*Acinetobacter* was reported as an efficient producer of selenium nanoparticles when cell suspension and total cell protein of the strain *Acinetobacter* sp. SW30 was used [25]. In our case, capacity of this microorganisms to produce CuNPs was established (Table 2).

Based on preliminary results of the tested bacteria to synthesize nanoparticles, production of the CuNPs in dynamics of the process was studied on example of *Pseudomonas* species. It was established that all studied strains possess the ability to synthesize nanoparticles to one degree or another and the maximum synthesis is observed after 48-72 h (Table 3).

Strains *Pseudomonas stutzeri* and *Pseudomonas* sp. 23 revealed the best CuNPs synthesizing capacity, moreover nanoparticles synthesized by these strains expressed stability for up to a fortnight (Table 3). Its possible reason may be the formation of smaller nanoparticles and synthesis of compounds, which envelop nanoparticles preventing their aggregation and by this, probably, stabilizes them as well. Formation of the CuNPs in the cultural liquid of *Pseudomonas*

strains was determined both visually and by UV-spectroscopy (Figures 3 and 4).

UV-spectroscopy analysis revealed that, with an increase in the concentration of copper (II) ions, a bathochromic shift of the absorption wavelength is observed, which is directly proportional to the size of the nanoparticles. It was established that copper nanoparticles are observed in the form spherical particles, elongated particles are observed as well. At the same time, majority of studied microbial cultures, both bacteria and actinomycetes, produced insignificant quantities of copper nanoparticles.


It was established that nanoparticles were observed mostly after 24-48 h depending on certain microorganism and the highest synthesizing activity was observed after 48-72 h for the most of the cultures. More extended contact with copper salt causes aggregation of nanoparticles and precipitation, especially this is true in case of microscopic fungi.

**Table 2.** Screening for CuNPs producing ability among selected bacterial strains.


No.	Culture	Cultivation time (h)		
		24	48	72
1.	<i>Pseudomonas putida</i>	+	+	-
2.	<i>Pseudomonas stutzeri</i>	+	2+	3+
3.	<i>Pseudomonas fluorescens</i>	+	+	+
4.	<i>Arthrobacter globiformis</i>	+	+	+
5.	<i>Bacillus megatherium</i>	+	2+	2+
6.	<i>Bacillus subtilis</i>	-	+	+
7.	<i>Bacillus</i> sp.	-	+	+
8.	<i>Acinetobacter</i> sp.	+	+	-+

**Table 3.** Screening of *Pseudomonas* strains for CuNPs synthesis.

Strain	Growth (days)					
	1	2	3	5	7	14
<i>Pseudomonas stutzeri</i>	+	3+	3+	3+	3+	3+
<i>Pseudomonas putida</i> 1	+	+	-	-	-	-
<i>Pseudomonas</i> sp. 23	+	2+	2+	2+	2+	+
<i>Pseudomonas</i> sp. R	+	+	+	+	+	+

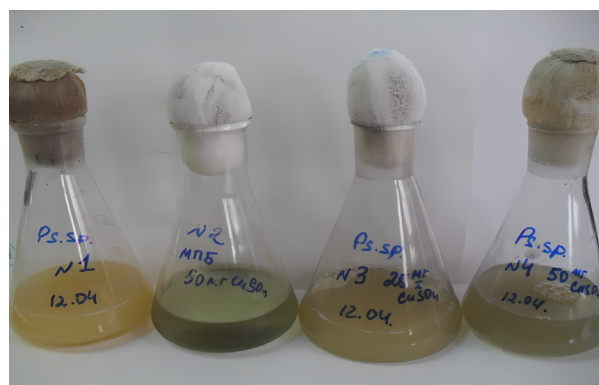

**Fig. 3.** Formation of CuNPs by strain *Pseudomonas* sp.: 1 – control (pure cultural liquid of the strain); 2 – BEP broth +  $\text{CuSO}_4$ ; 3 – cultural liquid of *Pseudomonas* sp. with added 25 mg/l of  $\text{Cu}^{2+}$ ; 4 – cultural liquid of *Pseudomonas* sp. with added 50 mg/l of  $\text{Cu}^{2+}$ .

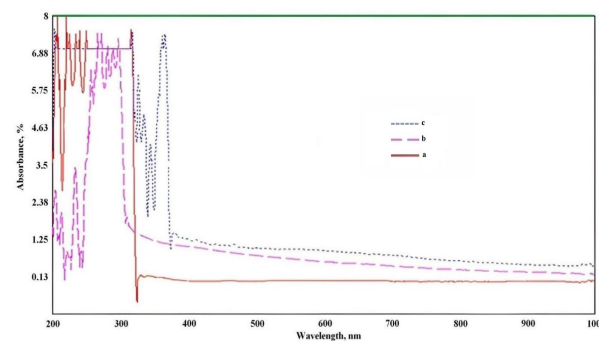

**Fig. 4.** UV-spectra of the systems with different amount of CuNPs: (a) beef extract peptone broth (BEPB); (b) BEPB+microorganism+ $\text{Cu}^{2+}$  (25 mg/l); (c) BEPB+microorganism+ $\text{Cu}^{2+}$  (50 mg/l).



#### 4. CONCLUSIONS

From the present study we can conclude that strains *Fusarium oxysporum* and *Penicillium* sp 2, and *Pseudomonas* species were the most active producers of copper nanoparticles among all screened culture collection strains. Biogenic production of copper nanoparticles by bacteria and fungi presents certain scientific and applied interest. Based on results of the UV-spectroscopy and AFS microscopy a database of microbial strains synthesizing copper nanoparticles was established, which may be used in future studies.

#### 5. CONFLICT OF INTEREST

The authors declare no conflict of interest.

#### 6. REFERENCES

1. K.L. Temple and N.W. Le Roux. Syngensis of sulfide ores; desorption of adsorbed metal ions and their precipitation as sulfides. *Economic Geology* 59(4): 647-655 (1964).
2. G. Shobha, V. Moses, and S. Ananda. Biological synthesis of copper nanoparticles and its impact. *International Journal of Pharmaceutical Science Invention* 3(8): 6-28 (2014).
3. R. Cuevas, N. Durán, M.C. Diez, G.R. Tortella, and O. Rubilar. Extracellular biosynthesis of copper and copper oxide nanoparticles by *Stereum hirsutum*, a native white-rot fungus from Chilean forests. *Journal of Nanomaterials* 2015: 789089 (2015).
4. R. Varshney, S. Bhadauria, and M.S. Gaur. A review: biological synthesis of silver and copper nanoparticles. *Nano Biomedicine & Engineering* 4(2): 99-106 (2012).
5. N.I. Hulkoti and T.C. Taranath. Biosynthesis of nanoparticles using microbes—a review. *Colloids and Surfaces B: Biointerfaces* 121: 474-483 (2014).
6. A.B. Moghaddam, F. Namvar, M. Moniri, S. Azizi, and R. Mohamad. Nanoparticles biosynthesized by fungi and yeast: a review of their preparation, properties, and medical applications. *Molecules* 20(9): 16540-16565 (2015).
7. K. Vijayaraghavan and T. Ashokkumar. Plant-mediated biosynthesis of metallic nanoparticles: a review of literature, factors affecting synthesis, characterization techniques and applications. *Journal of Environmental Chemical Engineering* 5(5): 4866-4883 (2017).
8. C.J. de Andrade, L.M. De Andrade, M.A. Mendes, and C.A.O. do Nascimento. An overview on the production of microbial copper nanoparticles by bacteria, fungi and algae. *Global Journal of Research in Engineering: C* 17(1): 27-33 (2017).
9. G.S. Dhillon, S.K. Brar, S. Kaur, and M. Verma. Green approach for nanoparticle biosynthesis by fungi: current trends and applications. *Critical Reviews in Biotechnology* 32(1): 49-73 (2012).
10. E. Dujardin, C. Peet, G. Stubbs, J.N. Culver, and S. Mann. Organization of metallic nanoparticles using tobacco mosaic virus templates. *Nano Letters* 3(3): 413-417 (2003).
11. A. Schröfel, G. Kratošová, M. Bohunická, E. Dobročka, and I. Vávra. Biosynthesis of gold nanoparticles using diatoms—silica-gold and EPS-gold bionanocomposite formation. *Journal of Nanoparticle Research* 13(8): 3207-3216 (2011).
12. G. Singaravelu, J. S. Arockiamary, V.G. Kumar, and K. Govindaraju. A novel extracellular synthesis of monodisperse gold nanoparticles using marine alga, *Sargassum wightii* Greville. *Colloids and Surfaces B: Biointerfaces* 57(1): 97-101 (2007).
13. A.K. Mittal, Y. Chisti, and U.C. Banerjee. Synthesis of metallic nanoparticles using plant extracts. *Biotechnology Advances* 31(2): 346-356 (2013).
14. R. Varshney, S. Bhadauria, M.S. Gaur, and R. Pasricha. Characterization of copper nanoparticles synthesized by a novel microbiological method. *JOM: The Journal of the Minerals, Metals & Materials Society* 62(12): 102-104 (2010).
15. R. Varshney, S. Bhadauria, M.S. Gaur, and R. Pasricha. Copper nanoparticles synthesis from electroplating industry effluent. *Nano Biomedicine and Engineering* 3(2): 115-119 (2011).
16. L.I. Zayinitdinova, R.N. Juraeva, N.A. Lazutin, A.M. Mavjudova, N.K. Bekmukhamedova, and R.B. Ergashev. Microbiocenosis of anthropogenically transformed soils. *Proceedings of the Pakistan Academy of Sciences: B Pakistan Academy of Sciences Life and Environmental Sciences*. 59(4): 15-23 (2022).
17. L.I. Zayinitdinova, R.N. Juraeva, J.J. Tashpulatov, S.I. Kukanova, N.A. Lazutin, and A.M. Mavjudova. Influence of silver and copper nanoparticles on the enzymatic activity of soil-borne microorganisms. *Baghdad Science Journal* 19(6): 1487-1492 (2022).
18. P. Mukherjee, S. Senapati, D. Mandal, A. Ahmad, M.I. Khan, R. Kumar, and M. Sastry. Extracellular synthesis of gold nanoparticles by the fungus

- Fusarium oxysporum*. *ChemBioChem* 3(5): 461-463 (2002).
19. A. Ahmad, P. Mukherjee, S. Senapati, D. Mandal, M.I. Khan, R. Kumar, and M. Sastry. Extracellular biosynthesis of silver nanoparticles using the fungus *Fusarium oxysporum*. *Colloids and Surfaces B: Biointerfaces* 28(4): 313-318 (2003).
  20. S. Honary, H. Barabadi, E. Gharaei-Fathabad, and F. Naghibi. Green synthesis of copper oxide nanoparticles using *Penicillium aurantiogriseum*, *Penicillium citrinum* and *Penicillium waksmanii*. *Digest Journal of Nanomaterials and Biostructures* 7(3): 999-1005 (2012).
  21. D.R. Majumder. Bioremediation: copper nanoparticles from electronic-waste. *International Journal of Engineering Science and Technology* 4(10): 4380- 4389 (2012).
  22. S.S. Birla, S.C. Gaikwad, A.K. Gade, and M. K. Rai. Rapid synthesis of silver nanoparticles from *Fusarium oxysporum* by optimizing physiocultural conditions. *The Scientific World Journal* 2013: 796018 (2013).
  23. O.V. Singh (Ed.). Bio-nanoparticles: biosynthesis and sustainable biotechnological implications. *John Wiley & Sons* (2015).
  24. R.K. Shah, A. Haider, and L. Das. Extracellular synthesis of ag nanoparticles using *Escherichia coli* and their antimicrobial efficacy. *International Journal of Pharmacy and Biological Sciences* 7: 78-83 (2017).
  25. S.A. Wadhwani, M. Gorain, P. Banerjee, U.U. Shedbalkar, R. Singh, G.C. Kundu, and B.A. Chopade. Green synthesis of selenium nanoparticles using *Acinetobacter* sp. SW30: optimization, characterization and its anticancer activity in breast cancer cells. *International Journal of Nanomedicine* 12: 6841-6855 (2017).
  26. Z. Lyudmila, V. Noira, R. Sayora, K. Svetlana, J. Rokhilya, and T. Javlon. Microbial Synthesis of Silver Nanoparticles by *Pseudomonas* sp. *BioTechnology: An Indian Journal* 14(4): 169 (2018).
  27. A.M. Pat-Espadas and F.J. Cervantes. Microbial recovery of metallic nanoparticles from industrial wastes and their environmental applications. *Journal of Chemical Technology & Biotechnology* 93(11): 3091-3112 (2018).
  28. B. Afzal, D. Yasin, S. Husain, A. Zaki, P. Srivastava, R. Kumar, and T. Fatma. Screening of cyanobacterial strains for the selenium nanoparticles synthesis and their anti-oxidant activity. *Biocatalysis and Agricultural Biotechnology* 21: 101307 (2019).
  29. M.P. Desai and K.D. Pawar. Immobilization of cellulase on iron tolerant *Pseudomonas stutzeri* biosynthesized photocatalytically active magnetic nanoparticles for increased thermal stability. *Materials Science and Engineering: C* 106: 110169 (2020).